The monoclinic phase of PZT ceramics: Raman and phenomenological theory studies

A. G. Souza Filho*, K. C. V. Lima, A. P. Ayala, I. Guedes, P. T. C. Freire and J. Mendes Filho
Departamento de Física, Universidade Federal do Ceará, Caixa Postal 6030, Campus do Pici, 60455-760 Fortaleza, Ceará, Brazil

E. B. Araújo and J. A. Eiras
Departamento de Física, Universidade Federal de São Carlos, Caixa Postal 676, 13565-670 São Carlos SP - Brazil

(February 1, 2008)

arXiv:cond-mat/9909061v3 30 Sep 1999

This work reports on the first Raman detection of the tetragonal → monoclinic phase transition in PZT ceramics near morphotropic phase boundary at low temperatures. The transition is characterized by changes in the frequency of lattice modes with the temperature. The results presented here confirm the previous one recently reported by Noheda *et al.* [5,6] using high-resolution synchrotron X-ray powder diffraction technique and dielectric measurements. The stability of the new phase is discussed within the framework of phenomenological Landau-Devonshire Theory.

Due to their remarkable technological importance, $PbZr_{1-x}Ti_xO_3$ ceramics have been for long time the subject of extensive experimental and theoretical studies. Its excellent piezoelectric, dielectric and ferroelectric properties lead this material to be one of the most important material used in electronic devices. Its properties depend strongly on its structural phase. The composition(x)-temperature(T) phase diagram of the PZT system was determined by Jaffe *et al.* [1] using X-ray diffraction measurements. At room temperature PZT presents several structures depending on the value of x, namely: ferroelectric tetragonal (C^1_{4v}), two rhombohedral phases (C^6_{3v} and C^1_{3v}), and antiferroelectric orthorhombic (C^8_{2v}) phases. Also, at high temperatures, PZT presents a paraelectric cubic phase (O^1_h). The phenomenological Landau-Devonshire theory developed by Haun *et al.* [2] explains the stability of all phases contained in the concentration(x)-temperature(T) phase diagram determined by Jaffe *et al.* [1].

The separation between rhombohedral and tetragonal phase is called morphotropic phase boundary (MPB) and occurs around x = 0.50 and 0.55, where the exact compositions which the transitions occur are strongly dependent on the sample fabrication method [3] and the grain sizes [4]. Many efforts have been concentrated in obtaining samples belonging to this region of phase diagram, because of the enhancement of their electromechanical response. So, recently, new features on the MPB were reported by Noheda et. al [5,6]. Their works report on the high-resolution synchrotron X-ray powder diffraction techniques and dielectric measurements in PZT ceramics with compositions slightly different from that of MPB region. The authors discovered a new ferroelectric monoclinic phase at low temperatures and proposed a preliminary modification in the well-known phase diagram reported by Jaffe et. al. [1]. The most probable space group for this new ferroelectric monoclinic phase is C^3_s which is a subgroup of C^1_{4v} and C^6_{3v} groups. This monoclinic phase exhibited by PZT at low temperatures would be the first example of a ferroelectric material with P^2_x=P^2_y≠P^2_z, where P^2_x, P^2_y, $P^2_z \neq 0$. [5]

The transition observed by Noheda *et al.* [5] was due to the use of synchrotron radiation which provides a higher-resolution diffraction pattern than that obtained by conventional X-ray radiation. Micro-Raman spectroscopy, which is quite useful to investigate a localized area in the probed sample with a spatial resolution of the order of μm, is very effective tool to study phase transitions in polycrystalline materials. Despite the works reported in Refs. [5] and [6] no study on the modifications of optical modes when PZT undergoes a phase transition from tetragonal to monoclinic were already presented. So, the aim of this work is to present a systematic micro-Raman study of PZT ceramics close to MPB in the temperature range from 25 to -240 ^oC, in order to reveal the behavior of optical phonons when PZT ceramics undergoes a phase transition from tetragonal to monoclinic structure. A preliminar analysis of the phase sequence, based on phenomenological Landau-Denvonshire theory, is also presented.

The sample $PbZr_{0.52}Ti_{0.48}O_3$ was obtained through the solid-state reaction from 99.9 % pure reagent grade PbO, ZrO_2 and TiO_2 oxides. The starting powders and distilled water were mixed and milled during 3.5 hours for powder homogenization. The mixture was calcined at 850 ^oC for 2.5 h. It was pressed at 400 MPa giving rise to PZT ceramics disks with 10 mm of diameter and 5 mm of thickness. Finally, the disks were sintered at temperature of 1250 ^oC during

*Corresponding Author: A. G. Souza Filho, FAX 55 (85) 2874138, E-mail: agsf@fisica.ufc.br

4h. The sintering atmosphere, which consists of a covered alumina crucible, was enriched in PbO vapor using $PbZrO_3$ powder around the disks in order to avoid significant volatilization of PbO.

MicroRaman measurements were performed using a T64000 Jobin Yvon Spectrometer equipped with an Olympus microsocope and a N_2- cooled CCD to detect scattered light. The spectra were excited with an Argon ion Laser (λ = 514.5 nm), and the power laser impinging on the samples surface is estimated to be of order of 10 mW. The spectrometer slits were set to give a spectral resolution of better than 2 cm^{-1}. A Nikon 20x objective with focal distance 20 mm and numeric apperture N.A. = 0.35 was employed to focus the laser beam on the polished sample surface. Low temperature measurements were performed using an Air Products closed-cycle refrigeration which provides temperatures ranging from 20 K to 300 K. An Eurotherm controller was used to control the temperature with precision of order of $\pm$0.1 K.

Raman spectra in the low frequency mode region of $PbZr_{0.52}Ti_{0.48}O_3$ ceramic recorded at several temperatures are presented in Fig. 1. First, let us discuss on the assignment of the Raman modes observed in the spectrum at room temperature. The spectral region below 150 cm^{-1} contains the external modes of the material and for PZT systems is related to Pb- lattice modes [7], while the region above 150 cm^{-1} contains the modes related to some internal modes (bending, torsion, and stretching) of certain groups of the material, e.g., $(Zr/Ti)O_6$ units. The Raman modes located at 25, 48, 94, and 136 cm^{-1} are labeled as A, B, C, and D, respectively. The mode at 50 cm^{-1} , which is absent in $PbTiO_3$, appears in bulk PZT ceramics for Zr content lower than 0.1, being considered an additional mode [4,8]. In our samples, this mode were found to be located at 48 cm^{-1}.

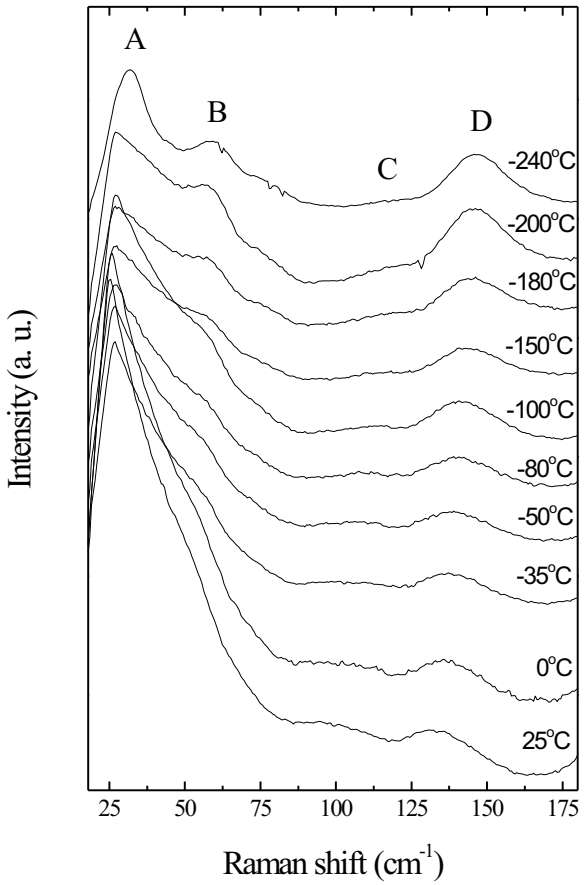

FIG. 1. Low frequency Raman spectra of $PbZr_{0.52}Ti_{0.48}O_3$ ceramics recorded in the temperature range from 25 to -240 ^oC.

Next, let us discuss on the temperature dependence of the frequency modes shown in Fig. 1. Particular attention was devoted to the modes A, B, and C. The mode B, which at room temperature appears to be coalesced with mode A, is clearly solved at low temperatures. In the temperature interval from -10 to -40 ^oC, it was observed changes in the frequency of mode C, which are depicted in Fig. 2. Such kind of behavior clearly indicates the existence of a phase transition, which following the works reported by Noheda *et al.* [5,6], changes the structure of PZT from tetragonal (C^1_{4v}) to monoclinic (C^3_s).

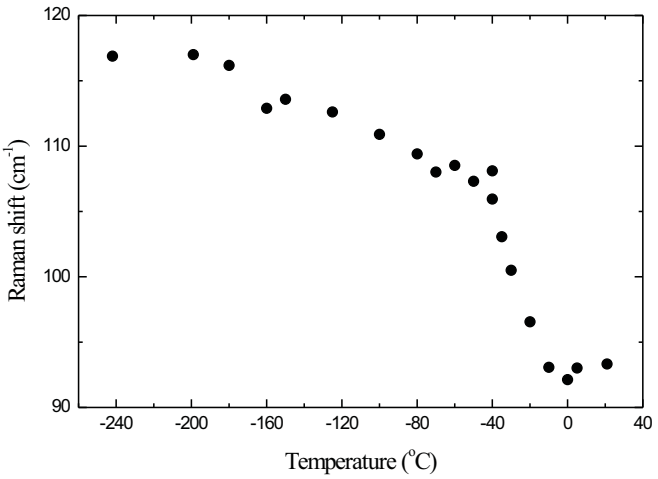

FIG. 2. Variation of the frequency of the Raman mode C as a function of temperature in the range from 25 to -240 ^oC. The anomaly observed clearly indicates the occurrence of a phase transition from tetragonal to monoclinic structure.

In order to discuss the stability of this new phase we use the Landau−Devonshire phenomenological theory. It should be remarked that, Haun and coworkers [2,9–12] have evaluated various coefficients related to the free energy function, developing a complete theory that describes the well-known phase transitions in the PZT system. In this work, we consider a simplified version of the free energy used in Ref.[2], since only polarization changes are involved in the phases separated by the MPB. In this case, the free energy, in absence of stress, is given by :

$$\begin{aligned}\Delta G = \alpha_1(P_1^2+P_2^2+P_3^2)+\alpha_{11}(P_1^4+P_2^4+P_3^4)+\alpha_{12}(P_1^2\,P_2^2+P_1^2\,P_3^2+P_2^2\,P_3^2)+\\ +\alpha_{111}(P_1^6+P_2^6+P_3^6)+\alpha_{112}(P_3^4(P_1^2+P_2^2)+P_2^4\,(P_1^2+P_3^2)+\\ +P_1^4\,(P_2^2+P_3^2))+\alpha_{123}P_1^2\,P_2^2\,P_3^2\end{aligned} \tag{1}$$

where P_i (i=1,2,3) is the polarization along the cubic axes, $\alpha_1, \alpha_{i,j}$ (i, j = 1,2), and $\alpha_{i,j,k}$ (i,j,k=1,2,3) are the dielectric stiffness and high-order dielectric stiffness at constant stress, respectively. Here α_1 is the only temperature dependent coefficient and it is given by the Curie-Weiss law ($\alpha_1 = (T - T_0)/C\epsilon_0$). As already mentioned, the values of all coefficients and the solutions for the tetragonal and rhombohedric phases can be found in Refs. [2] and [9-12]. Here, we present only the solutions for the monoclinic phase as proposed by Noheda *et al.* [5]. These authors stated that the cations displacements lie close to the monoclinic [$\bar{2}$01] direction, which corresponds to the rhombohedral [111] axis. As a consequence of this structure, the electric polarization have the following conditions: P_1^2=P_2^2≠P_3^2 and P_1^2, $P_3^2 \neq 0$. In this case, the free energy under zero stress reads

$$\begin{aligned}\Delta G_{FM} = \alpha_1(2P_1^2+P_3^2)+(2\alpha_{11}+\alpha_{12})P_1^4+\alpha_{11}P_3^4+2\alpha_{12}P_1^2P_3^2+2(\alpha_{111}+\alpha_{112})P_1^6+\\ +\alpha_{111}P_3^6+2\alpha_{112}P_1^2P_3^4+(2\alpha_{112}+\alpha_{123})P_1^4P_3^2\end{aligned} \tag{2}$$

As the free energy of the monoclinic phase has two order parameters, the spontaneous polarization can be found from the first partial derivative stability conditions: $\partial\Delta G_{FM}/\partial P_1 = 0$ and $\partial\Delta G_{FM}/\partial P_3 = 0$. Unfortunately, this is a system of nonlinear equations which does not have an analytical solution. Hence a numerical solution method was used to obtain the polarization and the free energy of the monoclinic phase. In Fig. 3 the free energy of the tetragonal, rhombohedric and monoclinic phases is plotted as a function of the Ti concentration at -80 ^oC. While Eq. [2] is able to predict the rhombohedric → tetragonal phase transition at approximately x=0.5, the calculations clearly

shows that the monoclinc phase is not stable for any value of Ti concentration. This result indicates that Eq. (2) is not suitable to describe the existence of monoclinic phase. To describe the monoclinic phase we take into account a third order parameter, which in accordance with Ref. 6, is the monoclinic angle β. In fact, the monoclinic angle β is not the true order parameter since it does not go to zero at T=T$_M$, where T$_M$ is the temperature of tetragonal $\rightarrow$ monoclinic phase transition. The true order parameter should be $90^o - \beta$. However, we will maintain the notation β for the third order parameter. With this, the PZT system in the monoclinic phase has the characteristic of an improper ferroelectric [13] and the free energy is now given by:

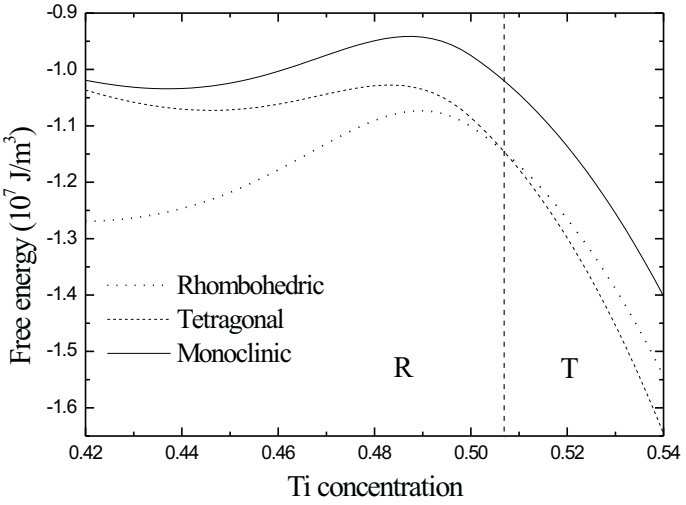

FIG. 3. Plot of free energy as a function of Ti concentration for the rhombohedric (R), tetragonal (T) and monoclinic (M) solutions at T=-80^oC . The capital letters indicated the low energy phase in each region.

$$\Delta G_{IM} = \Delta G_{FM} + \eta_1(T - T_M)\beta^2 + \eta_{11}\beta^4 + \phi\beta^2(2P_1^2 + P_3^2) \tag{3}$$

Unfortunately, there is no much information about the new monoclinic phase. So we do not have the experimental data necessary to calculate the values of the free energy coefficients. However, to verify that Eq. (3) is able to predict the existence of the monoclinic phase, we will make some rough approximations to estimate these coefficients. First, we will suppose that the coupling coefficient between β and the polarization (ϕ) is negligible compared with the dielectric stiffness coefficient (α_1). With this supposition, the first partial derivative stability condition read

$$\partial\Delta G_{IM}/\partial P_1 \simeq \partial\Delta G_{FM}/\partial P_1 = 0 \tag{4}$$

$$\partial\Delta G_{IM}/\partial P_3 \simeq \partial\Delta G_{FM}/\partial P_3 = 0 \tag{5}$$

$$\partial\Delta G_{IM}/\partial\beta = 2\beta(\eta_1(T - T_M) + \phi(2P_1^2 + P_3^2) + 2\eta_{11}\beta^2) = 0 \tag{6}$$

Thus, the polarization values obtained by minimizing the Eq. 2 can be used to calculate the third order parameter, that is

$$\beta^2 = -\frac{\eta_1}{2\eta_{11}}(T - T_M + \frac{\phi}{\eta_1}(2P_1^2 + P_3^2)) \tag{7}$$

Replacing Eq. (7) into Eq. (3), we find the modified free energy in the monoclinic phase, namely

$$\Delta G_{IM} = \Delta G_{FM} - \frac{\eta_1^2}{4\eta_{11}}(T - T_M + \frac{\phi}{\eta_1}(2P_1^2 + P_3^2))^2 \tag{8}$$

Next, we can use the few available data to estimate the unknown coefficients. By using the temperature dependence of β obtained by Noheda *et al.* [6] and Eq. (7), we calculated that the ϕ/η_1 ratio is $\approx 10^3$ m^{2o}C/C. Furthermore, we

assumed a linear dependence of the transition temperature between the values obtained for Ti concentrations between 0.48 and 0.50. Finally, the $\eta_1^2/4\eta_{11}$ ratio necessary for the Eq. 8 could be approximately found by considering that the tetragonal and monoclinic free energies should be equal on the phase transition ($x \simeq 0.48$ and $T_M \simeq$ -40 ^oC; $x \simeq 0.50$ and $T_M \simeq$ -80 ^oC). This calculation yielded an approximate value of $\eta_1^2/4\eta_{11} \simeq 5$ J/^{o}C^{2}m^3. By using this estimated parameter, we were able to calculate the dependence concentration of the modified free energy. In Fig. 4 we compare the modified free energy with those of other phases of PZT. It should be observed that the value of the free energy of the monoclinic phase is lower than that of free energy of the rhombohedric and tetragonal phases in a small region close to MPB. This result shows that the modified free energy correctly predicts the existence of a monoclinic phase in the MPB region, in accordance with the experimental observations.

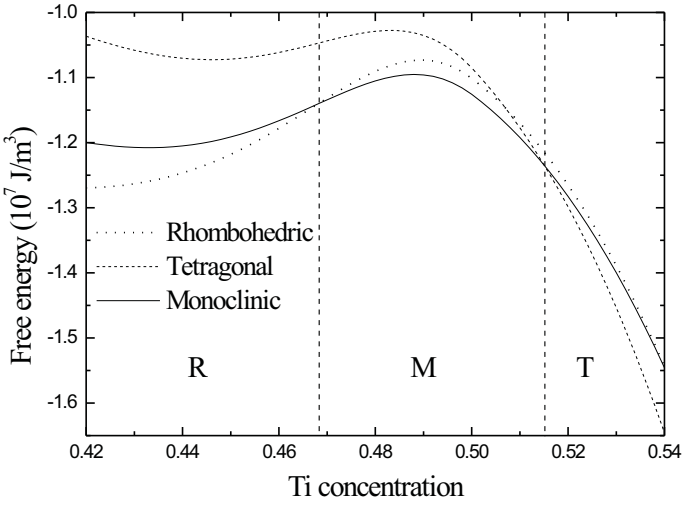

FIG. 4. Plot of free energy as a function of Ti concentration for the rhombohedric (R), tetragonal (T) and monoclinic (M) solutions at T=-80^oC . The capital letters indicated the low energy phase in each region.

In conclusion, the changes in the frequency of the mode labeled by C when temperature is varied from 25 to -240 ^oC, indicates that PZT undergoes a phase transition from tetragonal to monoclinic structure. This result agrees well with those recently reported by Noheda *et al.* [5,6] using high resolution synchrotron X-ray powder diffraction techniques and dielectric measurements. We were able to describe this phase transition based on the Landau-Devonshire phenomenological theory. For this we introduced as a new order parameter the variable $90^o - \beta$, where β is the monoclinic angle. Using the scarce experimental data available we estimated the modified free energy coefficients. Calculations carried out with the modified free energy confirmed that the monoclinic phase is stable in a thin region close to MPB.

Acknowledgements – Financial support from FUNCAP, CNPq, FAPESP and FINEP is grateful acknowledged. One of us, A. G. Souza Filho wishes to acknowledge the fellowship received from FUNCAP.

---

[1] B. Jaffe, W.R. Cook, and H. Jaffe, in *Piezoelectric Ceramic*, Academic Press, New York, 1971.
[2] M. J. Haun, E. Furman, S. J. Jang, and L. E. Cross, Ferroelectrics **99**, 13 (1989).
[3] K. Kakewaga, O. Matsunaga, T. Kato, and Y. Sasaki, J. Am. Ceram. Soc. **78**, 1071 (1995).
[4] J. F. Meng, R. S. Katiyar, G. T. Zou, and X. H. Wang, phys. stat. sol. (a) **164**, 851 (1997).
[5] B. Noheda, D. E. Cox, G. Shirane, J. A. Gonzalo, S.E. Park and L. E. Cross, Appl. Phys. Lett. **74**, 2059 (1999).
[6] B. Noheda, J.A. Gonzalo, A. Caballero, C. Moure, D.E. Cox, G. Shirane. To be published in Ferroelectrics. (http://xxx.lanl.gov/abs/cond-mat/9907286)

[7] C. Carabatos-Nedelec, I. El Harrad, J. Handerek, F. Brehat, and B. Wyncke, Ferroelectrics **125**, 483 (1992).
[8] R. Merlin, J. A. Sanjurjo, and A. Pinezuk, Solid State Commun. **16**, 931 (1975).
[9] M. J. Haun, E. Furman, H. A. McKinstry, and L. E. Cross, Ferroelectrics **99**, 27 (1989).
[10] M. J. Haun, Z. Q. Zhuang, E. Furman, S. J. Jang, and L. E. Cross, Ferroelectrics **99**, 45 (1989).
[11] M. J. Haun, E. Furman, T. R. Halemane, and L. E. Cross, Ferroelectrics **99**, 55 (1989).
[12] M. J. Haun, E. Furman, S. J. Jang, and L. E. Cross, Ferroelectrics **99**, 63 (1989).
[13] B. A. Strukov and A. P. Levanyuk, *Ferroelectric Phenomena in Crystals: Physical Foundations*, Springer (1997).